Feeds and Speeds for RAKU® TOOL WB-0801

RAMPF discover the future

formula for calculating speed (spindle)

$$n = \frac{V_c \times 12{,}0001}{D_c \times \pi}$$

15715 [rpm] = $\frac{3084 \text{ [ft/min]} \times 12{,}0001}{¾ \text{ [in]} \times 3{,}14}$

formula for calculating axis feed rate

$$V_f = n \times f_z \times z_n$$

619 [in/min] = 15715 [rpm] x 0,0197 [in] x 2 [number]

validated cutting data for roughing

Type	D_c [in]	z_n [number]	V_c [ft/min]	f_z [in]	n [rpm]	V_f [in/min]	a_e [in]	a_p [in]	L_1 [in]	L_2 [in]
torus	¾	2	3084	0,0197	15.715	619	0,394	0,787	3,386	0,787
torus	½	2	1837	0,0189	14.043	531	0,236	0,472	2,165	0,630
torus	¼	2	919	0,0189	14.043	531	0,118	0,236	0,906	0,315

validated cutting data for finishing

Type	D_c [in]	z_n [number]	V_c [ft/min]	f_z [in]	n [rpm]	V_f [in/min]	a_e [in]	a_p [in]	L_1 [in]	L_2 [in]
ball	¾	2	3084	0,0240	15.715	755	0,008	0,079	2,638	0,669
ball	½	2	1837	0,0240	14.043	675	0,005	0,047	2,047	0,413
ball	¼	2	919	0,0240	14.043	675	0,002	0,024	0,906	0,394

recommended cutting data for roughing

parameter	symbol	unit	roughing recommendation min.	roughing recommendation ideal	roughing recommendation max.
radial infeed:	a_e	[in]	- x D_c	**0.50 x D_c**	0.80 x D_c
axial infeed:	a_p	[in]	0.10 x D_c	**1.00 x D_c**	2.00 x D_c
number of teeth:	z_n	[number]	1	**2**	4

recommended cutting data for finishing

parameter	symbol	unit	finishing recommendation min.	finishing recommendation ideal	finishing recommendation max.
radial infeed:	a_e	[in]	- x D_c	**0.01 x D_c**	0.10 x D_c
axial infeed:	a_p	[in]	0,01 x D_c	**0.10 x D_c**	0.50 x D_c
number of teeth:	z_n	[number]	1	**2**	4

parameter	symbol	unit	user specifications
cutting speed:	V_c	[ft/min]	selection in the diagram
feed/tooth:	f_z	[in]	selection in the diagram
speed (spindle):	n	[rpm]	calculation by user
axis feed rate:	V_f	[in/min]	calculation by user
cutting diameter:	D_c	[in]	processing specific
tool total length:	L_0	[in]	processing specific
tool unclamping length:	L_1	[in]	processing specific
tool cutting length:	L_2	[in]	processing specific

RAMPF Group, Inc.

49037 Wixom Tech Drive I Wixom, MI 48393, USA
T +1.248.295.0223 I F +1.248.295.0224
E info.us@rampf-group.com

Feeds and Speeds for
RAKU® TOOL WB-0801

RAMPF
discover the future

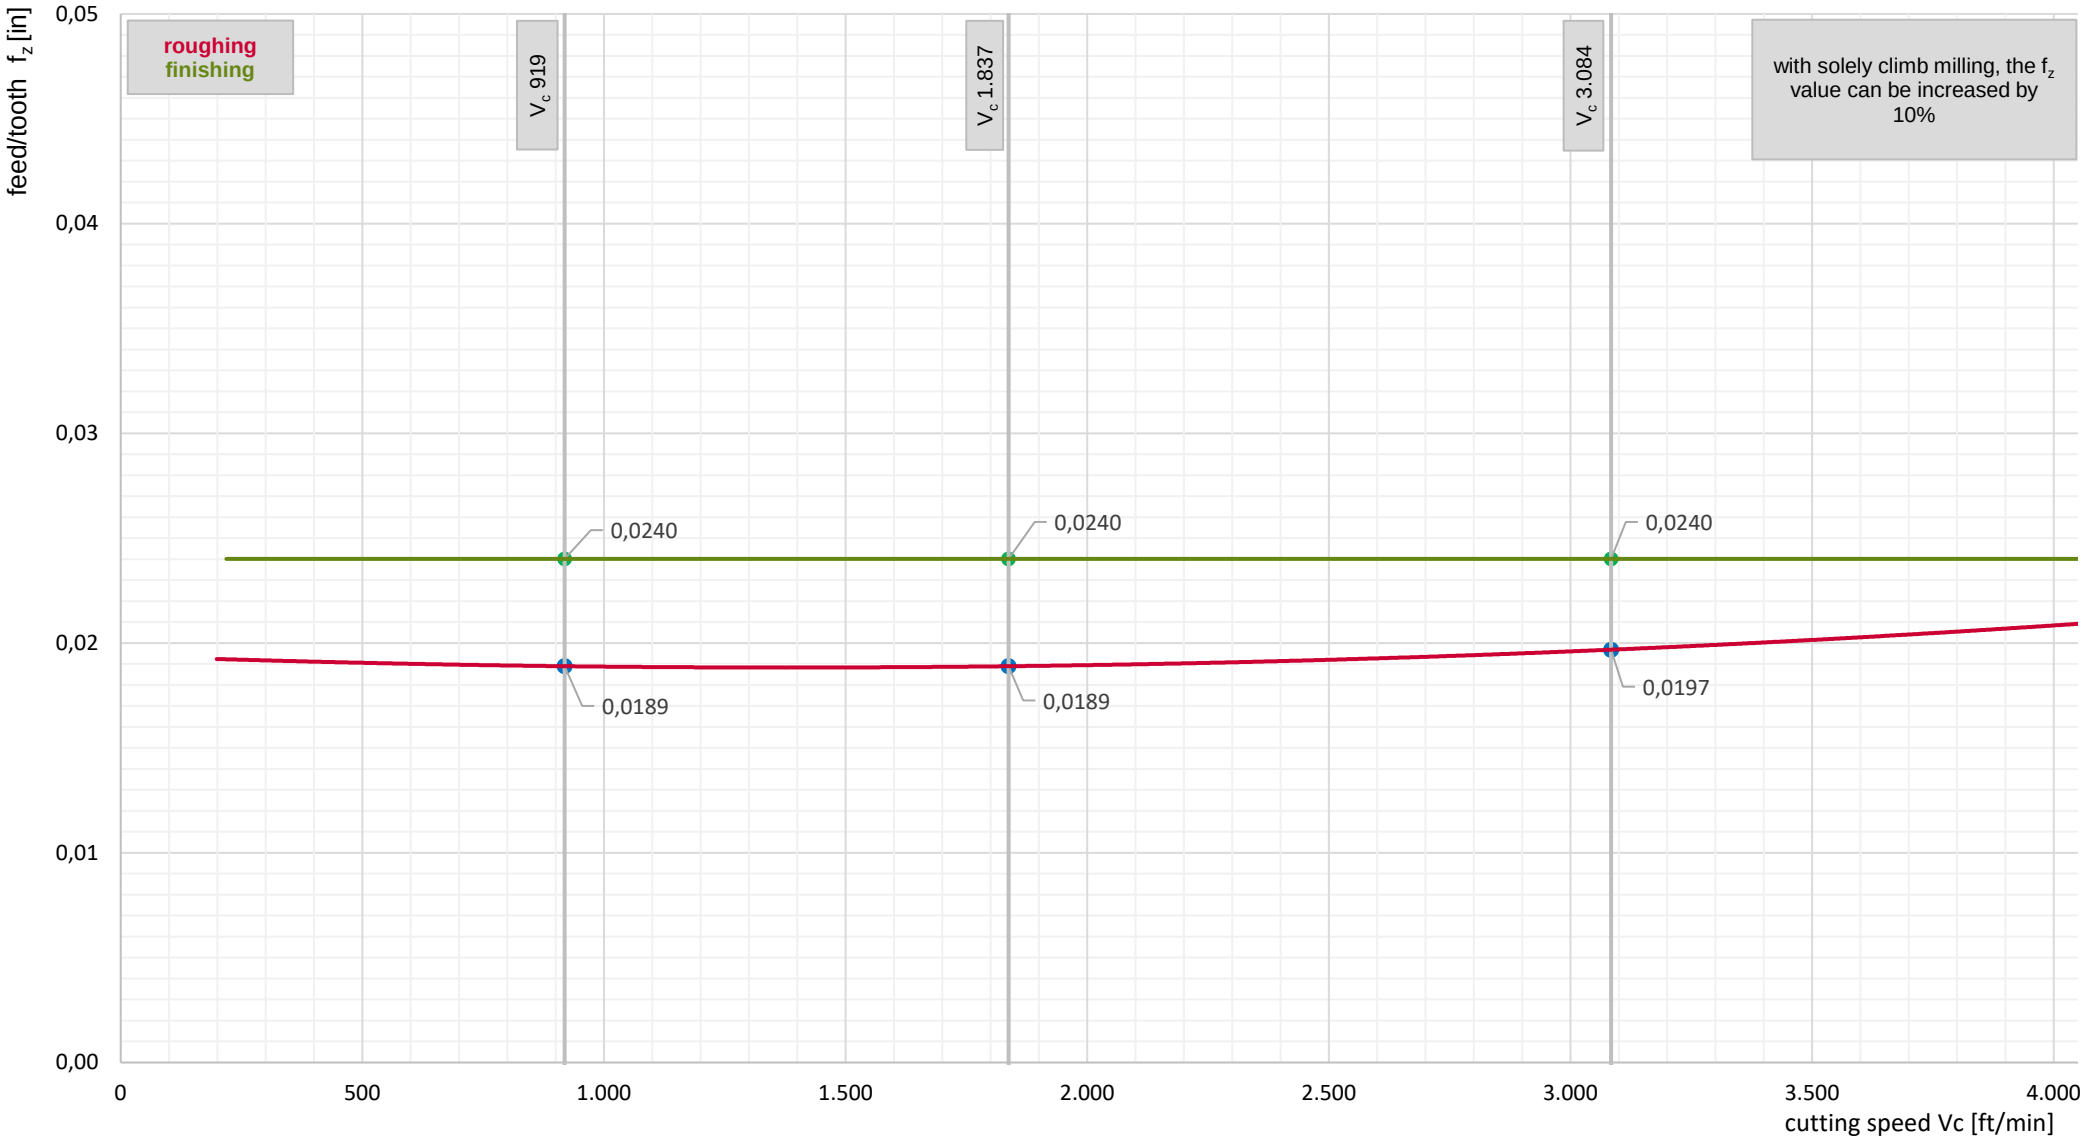

RAMPF Group, Inc.

49037 Wixom Tech Drive I Wixom, MI 48393, USA
T +1.248.295.0223 I F +1.248.295.0224
E info.us@rampf-group.com

Feeds and Speeds for
RAKU® TOOL WB-0801

RAMPF
discover the future

cutting data used on the demonstrator

sequence of processing	processing strategy	a_e [in]	a_p [in]	offset [in]	f_z [in]	V_c [ft/min]
roughing torus D6	vol. roughing following contour	0,118	0,236	0,024	0,019	919
roughing torus D12	vol. roughing following contour	0,236	0,472	0,005	0,019	1837
roughing torus D20	vol. roughing following contour	0,394	0,787	0,079	0,020	3084
finishing ball D6	zigzag stroke milling	0,002	0,024	0,000	0,024	919
finishing ball D12	zigzag stroke milling	0,005	0,047	0,000	0,024	1837
finishing ball D20	zigzag stroke milling	0,008	0,079	0,000	0,024	3084

tools used on the demonstrator

tool manufacturer	tool type	D_c [in]	L_0 [in]	L_1 [in]	L_2 [in]	z_n [number]
hufschmied-tools.com/de/	PROTO-LINE / torus	¼	2,36	0,91	0,31	2
hufschmied-tools.com/de/	PROTO-LINE / torus	½	3,94	2,17	0,63	2
hufschmied-tools.com/de/	PROTO-LINE / torus	¾	4,09	3,39	0,79	2
hufschmied-tools.com/de/	PROTO-LINE / ball	¼	2,36	0,91	0,39	2
hufschmied-tools.com/de/	PROTO-LINE / ball	½	3,27	2,05	0,41	2
hufschmied-tools.com/de/	PROTO-LINE / ball	¾	4,09	2,64	0,67	2

RAMPF Group, Inc.

49037 Wixom Tech Drive I Wixom, MI 48393, USA
T +1.248.295.0223 I F +1.248.295.0224
E info.us@rampf-group.com